

Effect of temperature on the binding energy of a shallow hydrogenic impurity in a Quantum Well Wire

T G Emam

Department of Mathematics, Faculty of science, Ain Shams university,
Abbassia, Cairo, Egypt.

and

Department of Mathematics, the German university in Cairo-GUC, New
Cairo city, Main Entrance Al Tagamoa Al Khames, Egypt.

Abstract

This work studies the effect of temperature on the binding energy of a shallow hydrogenic impurity located on the axis of a cylindrical semiconductor $GaAsAl_xGa_{1-x}As$ quantum well wire. The results show that the binding energy at a low temperature of $100K$ is increased by about 11% over that associated with nearly room temperature, $300K$, and is also increased by about 23% over that associated with temperature of $500K$.

1 Introduction

The electronic properties of a hydrogenic impurity in the quantum well[1,2,3,4] and the quantum well wire(QWW)[5,6,7,8,9,10] has been the subject of many articles . The binding energy of a shallow hydrogenic impurity in a quantum well wire has been calculated as a function of the wire radius [5]. It has been found that the binding energy increases with decreasing the wire radius for an infinite well whereas it reaches a peak value and then diminishes to a limiting value for a finite potential. The effect of location [6,7] of impurities has been studied as well as the different shapes of the cross-section [6,7] of the wire. Chen et al [11] have studied the effect of electron-phonon interaction on the impurity binding energy in a quantum wire .

In this work, the effect of temperature on the binding energy of a donor impurity confined in a QWW is investigated theoretically using a variational method .

2 Theory

The Hamiltonian for an on-axis hydrogenic impurity in a cylindrical infinite QWW of radius R is given by

$$H = \frac{-\hbar^2 \nabla^2}{2m_{1,2}(T)} - \frac{e^2}{\epsilon_{1,2}(T)\sqrt{\rho^2 + z^2}} + V_b(T), \quad (1)$$

where $m_{1,2}(T)$ and $\epsilon_{1,2}(T)$ are the temperature dependent effective-mass and dielectric constant of the QWW respectively. The two subscripts 1, 2 stand for the potential well (GaAs) and the potential barrier ($Al_xGa_{1-x}As$) materials respectively. The values of $m_{1,2}(T)$ and $\epsilon_{1,2}(T)$ are taken as given in Refs.[12] and [13]. The potential barrier height $V_b(T)$ is obtained from the temperature dependent band-gap discontinuity $\Delta E_g(x, T)$ given in eV as

$$V_b(T) = \begin{cases} 0, & \rho \leq R \\ 0.60\Delta E_g(x, T), & \rho > R, \end{cases} \quad (2)$$

where

$$\Delta E_g(x, T) = x[1.247 - (1.15 \times 10^{-4})T]; \quad x < 0.45. \quad (3)$$

The aim is to find the binding energy of the impurity using variational method

2.1 Electron Eigenstates

Considering the absence of impurity and imposing the boundary condition ; Continuity of the wavefunction and its first derivative at The QWW radius; the ground state wavefunction is found to be [5]:

$$\Psi(\rho) = \begin{cases} NJ_0(r_{10}\rho), & \rho \leq R \\ NJ_0(r_{10}R)\frac{K_0(b_{10}\rho)}{K_0(b_{10}R)}, & \rho > R \end{cases} \quad (4)$$

where N is the normalization constant, and

$$r_{10} = \sqrt{\frac{2m_1 E_{100}}{\hbar^2}}, \quad (5)$$

and

$$b_{10} = r_{10} \frac{J_1(r_{10}R)K_0(r_{10}R)}{J_0(r_{10}R)K_1(r_{10}R)}, \quad (6)$$

and the eigenenergy is

$$E_{100} = \frac{\hbar^2}{2m_1} r_{10}^2 = V_b(T) - \frac{\hbar^2}{2m_2} b_{10}^2. \quad (7)$$

The continuity of the derivative of the wave function wavefunction $\psi(\rho)$ at $\rho = R$ gives the equation

$$r_{10} \left(\frac{m_2(T)}{m_1(T)} \right) J_1(r_{10}R) = b_{10} \frac{J_0(r_{10}R)}{K_0(b_{10}R)} K_1(b_{10}R), \quad (8)$$

using Equation(7),and putting the length in the bohr radius units ($a_B = \frac{\epsilon_0 \hbar^2}{m_e e^2}$) and the energy in the Rydberg units ($R_b = \frac{e^2}{2\epsilon_0 a_B}$), where m_e is the electron effective mass in room temperature.

We get

$$r_{10} = \frac{J_0(r_{10}R)K_1(b_{10}R)}{J_1(r_{10}R)K_0(b_{10}R)} \sqrt{V_b(T) \frac{m_1^2(T)}{m_2(T)m_e} - \frac{r_{10}^2 m_1(T)}{m_2(T)}} \quad (9)$$

the first root of this equation for a certain temperature and wire radius gives the value of r_{10} , and hence the energy eigenvalue E_{100}

2.2 Impurity Eigenstates

Now we consider an on-axis hydrogenic impurity, the Schrödinger equation is no longer separable and the trial wave function is taken as

$$\Psi(\rho) = \begin{cases} N J_0(r_{10}\rho) \exp(-\lambda \sqrt{\rho^2 + z^2}), & \rho \leq R \\ N J_0(r_{10}R) \frac{K_0(b_{10}\rho) \exp(-\lambda \sqrt{\rho^2 + z^2})}{K_0(b_{10}R)}, & \rho > R \end{cases} \quad (10)$$

The normalization constant N is given by

$$N^{-2} = -2\pi \frac{d}{d\lambda} (A + B) \quad (11)$$

where

$$A = \int_{\rho=0}^{\rho=R} d\rho \rho J_0^2(r_{10}R) K_0(2\lambda\rho) \quad (12)$$

and

$$B = \frac{J_0^2(r_{10}R)}{K_0^2(b_{10}R)} \int_{\rho=R}^{\rho=\infty} d\rho \rho K_0^2(b_{10}R) K_0(2\lambda\rho). \quad (13)$$

Calculating the Potential energy $\langle V \rangle$ and the kinetic energy $\langle K.E \rangle$, it is found that

$$\langle V \rangle = -4\pi e^2 N^2 \left(\frac{A}{\epsilon_1(T)} + \frac{B}{\epsilon_2(T)} \right) - 2\pi N^2 V_b(T) \frac{dB}{d\lambda}, \quad (14)$$

and

$$\begin{aligned} \langle K.E \rangle = & - 2\pi N^2 \lambda^2 \left(\frac{\hbar^2}{2m_e} \right) \left(\frac{m_e}{m_1(T)} \frac{dA}{d\lambda} + \frac{m_e}{m_2(T)} \frac{dB}{d\lambda} \right) \\ & - 2\pi N^2 \left(\frac{\hbar^2}{2m_e} \right) \left(\frac{m_e}{m_1(T)} r_{10}^2 \frac{dA}{d\lambda} - \frac{m_e}{m_2(T)} b_{10}^2 \frac{dB}{d\lambda} \right) \\ & + 2\pi N^2 \left(\frac{\hbar^2}{2m_e} \right) (2\lambda R^2) [K_0(2\lambda R) J_0^2(r_{10}R) \left(\frac{m_e}{m_1(T)} - \frac{m_e}{m_2(T)} \right)] \end{aligned} \quad (15)$$

but

$$V_b(T) = \frac{\hbar^2 r_{10}^2}{2m_1(T)} + \frac{\hbar^2 b_{10}^2}{2m_2(T)}, \quad (16)$$

The total energy $E(R, T) = \langle T \rangle + \langle K.E \rangle$ can be obtained using equations(14),(15),(16)together with equation (11)

$$\begin{aligned} E(R, T) = & \frac{m_e}{m_1(T)} r_{10}^2 + \frac{\lambda^2 \left(\frac{m_e}{m_1(T)} \frac{dA}{d\lambda} + \frac{m_e}{m_2(T)} \frac{dB}{d\lambda} \right) + 4 \left(\frac{\epsilon_0}{\epsilon_1(T)} A + \frac{\epsilon_0}{\epsilon_2(T)} B \right)}{\frac{dA}{d\lambda} + \frac{dB}{d\lambda}} \\ & - \frac{2\lambda R^2 \left(\frac{m_e}{m_1(T)} - \frac{m_e}{m_2(T)} \right) (K_0(2\lambda R) J_0^2(r_{10}R))}{\frac{dA}{d\lambda} + \frac{dB}{d\lambda}} \end{aligned} \quad (17)$$

in the last equation we put the length in the bohr radius units a_B and the energy in the Rydberg units R_b .

The binding energy $E_b(R, T) = \frac{\hbar^2 r_{10}^2}{2m_e}$ is then given by:

$$\begin{aligned} E_b(R, T) = & - \frac{\lambda^2 \left(\frac{m_e}{m_1(T)} \frac{dA}{d\lambda} + \frac{m_e}{m_2(T)} \frac{dB}{d\lambda} \right) + 4 \left(\frac{\epsilon_0}{\epsilon_1(T)} A + \frac{\epsilon_0}{\epsilon_2(T)} B \right)}{\frac{dA}{d\lambda} + \frac{dB}{d\lambda}} \\ & + \frac{2\lambda R^2 \left(\frac{m_e}{m_1(T)} - \frac{m_e}{m_2(T)} \right) (K_0(2\lambda R) J_0^2(r_{10}R))}{\frac{dA}{d\lambda} + \frac{dB}{d\lambda}} \end{aligned} \quad (18)$$

According to the variational method, the right-hand side of the last equation is maximized with respect to λ to obtain a lower bound of the binding energy.

3 Results and Discussions

Figure (1) shows the dependence of the binding energy on the wire radius R for three different values of temperatures, $T = 100K$, $T = 300K$, and $T = 500K$, at aluminium concentration $x = 0.3$. At a given temperature the binding energy has a peak at a certain value of the wire radius, R_{max} , for this value the Coulomb interaction between the electron and the impurity is maximum due to the high localization of the wave function inside the well. For $R > R_{max}$ the binding energy decreases since the electron becomes less confined to the impurity due to the fact that the wave function becomes more spread out over the well. For $R < R_{max}$ the probability of finding the electron outside the well increases, the wave function penetrates through the surrounding barrier region, which leads to decrease the binding energy. The results shown in figure (1) show also that the difference between the binding energy at a temperature of $100K$ and that corresponds to a temperature of $300K$ for a QWW radius of $0.05a_B$ is about 11%. While this difference is about 23% in case of $T = 100K$ and $T = 500K$. In fact, this difference decreases by increasing the wire radius.

Figure (2) shows how the binding energy varies with the temperature for a certain value of the wire radius, $R = 0.5a_B$, at three values of aluminium concentration $x = 0.15$, $x = 0.30$, and $x = 0.45$, it can be concluded from figure (2) that the binding energy increases by decreasing the temperature and increasing the aluminium concentration, x . Increasing the value of x means increasing the value of the potential barrier, which in turns leads to a stronger confinement of the electron inside the QWW, and consequently greater binding energy.

4 Conclusion

The effect of temperature on the binding energy of a shallow hydrogenic impurity in a QWW is important and it should be taken into consideration. It is also found there is enhancement in this binding energy as the temperature

is lowered for a certain QWW radius.

References

- [1] Bastard G , Phys. Rev.B **24**, 4718 (1981).
- [2] Mailhiot C, Chang Y C, and McGill T C , Phys. Rev.B **26**, 4449 (1982).
- [3] Greene R L and Bajaj K K, Solid State Commun. **45**, 825 (1983).
- [4] Liu W M and Quinn J J, Phys. Rev.B **35**,2348 (1985).
- [5] Brown J W and Spector H N,J.Appl.Phys.,**59**, 1179 (1986).
- [6] Bryant G W, Phys. Rev.B **29**, 6632 (1984);**B31**,7812 (1985).
- [7] Branis S V, Li G, and Bajaj K K,, Phys. Rev.B **47**, 1316 (1993).
- [8] Bryant G W, Phys. Rev.B **37**, 8763 (1988).
- [9] Lee J and Spector H N, J.Appl.Phys.**54**, 3921 (1983);**57**,366(1985).
- [10] Chuu D S, Hsio C M and Mei W N, Phys. Rev.B **46**, 3898 (1992).
- [11] Chen Y N,Chuu D S,and Lin Y K, Physica B **291**, 228 (2000).
- [12] Elabsy A M, Physica Scripta **46**, 473 (1992).
- [13] Sarma G a, Phys. Rev.B **27**, 3494 (1983).

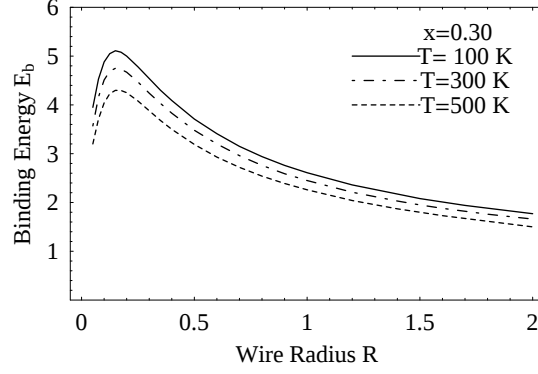


Figure 1: Variation of the binding energy E_b , in Rydberg (R_b) units as a function of the wire radius R , in Bohr radius units (a_B) at $x=0.30$, for three Different values of temperature, $T=100$ K (Solid curve), $T=300$ K (dashed-dotted curve), and $T=500$ K (Dotted curve).

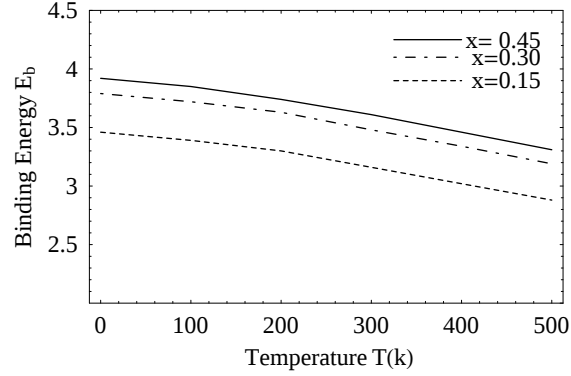


Figure 2: Variation of the binding energy E_b , in Rydberg (R_b) units as a function of the temperature T , in K, at a wire radius of $1a_B$, for three Different values of aluminium concentration, $x=0.45$ (Solid curve), $x=0.30$ (dashed-dotted curve), and $x=0.15$ (Dotted curve).